arXiv:cond-mat/0504766v1 [cond-mat.supr-con] 28 Apr 2005

Theory of superconducting pairing near the mobility edge

M. V. Feigel'man[1], L. B. Ioffe[2,1] and E. A. Yuzbashyan[2]
[1] *L. D. Landau Institute for Theoretical Physics, Kosygin str.2, Moscow 119334, Russia and*
[2] *Serin Physics Laboratory, Department of Physics and Astronomy, Rutgers University, Piscataway, NJ 08854, USA*
(Dated: February 2, 2008)

We develop a theory of a pseudogap state appearing near the superconductor-insulator transition in strongly disordered metals with attractive interaction. We show that such an interaction combined with the fractal nature of the single particle wave functions near the mobility edge leads to an anomalously large single particle gap in the superconducting state near SI transition that persists and even increases in the insulating state long after the superconductivity is destroyed. We give analytic expressions for the value of the pseudogap in terms of the inverse participation ratio of the corresponding localization problem.

A rapidly growing number of experiments[1,2,3,4,5,6,7,8,9] on various disordered superconductors show that a novel phase appears in the vicinity of the superconductor-insulator transition as sketched in the low temperature phase diagram in Fig. 1. On the superconducting side of the transition a relatively small magnetic field suppresses the superconductivity leading to an insulator characterized by a large thermally assisted resistance with a hard gap. Upon a further increase of the magnetic field the resistance and the gap drop[4,5,6,7,8]. It is tempting to explain these data by a formation of localized Cooper pairs[10] – in this picture the superconductivity is due to a fragile coherence between localized Cooper pairs, while the energy of single electron excitations is much larger and remains finite even when the coherence (and thus the superconductivity) is destroyed. Experimentally, this behavior is observed only for a limited range of disorder strengths, $\sigma_1 < \sigma < \sigma_2$, characterized by the conductivity σ at room temperature. At weaker disorder, $\sigma \geq \sigma_2$, the destruction of superconductivity by a magnetic field leads, as usual, to a formation of a normal metallic state without any noticeable localization effects. At larger disorder $\sigma < \sigma_1$ superconductivity is replaced by a gapped insulator even at $B = 0$. Usual insulator with a variable-range hopping conductance is recovered at larger disorder, $\sigma < \sigma_0$.

The hypothesis of preformed Cooper pairs is further confirmed by the behavior of disordered superconductors at higher temperatures. On the insulating side of the transition in thick (effectively 3D) films one observes[1,3] Arrenius behavior, $R(T) \propto \exp(T_I/T)$, at low temperatures. The experimental value of the activation energy, T_I, is somewhat larger than the superconducting gap in less disordered samples and grows with the disorder. For instance in InO_x films $T_I = 2 - 15\,K$, while the critical temperature $T_c = 3.3\,K$ in best samples[1,3]. However, at higher temperatures ($T \geq 10K$ for InOx films studied in Ref. 3) this behavior is replaced by Mott's variable range hopping $R(T) \sim \exp(T_M/T)^{1/4}$. Thus, qualitatively the temperature plays the same role as the magnetic field, suppressing an unconventional insulator formed near superconductor-insulator transition. This can be easily understood if the insulating pseudogap is due to preformed Cooper pairs with a pairing energy somewhat larger than the superconductive gap in a less disordered samples.

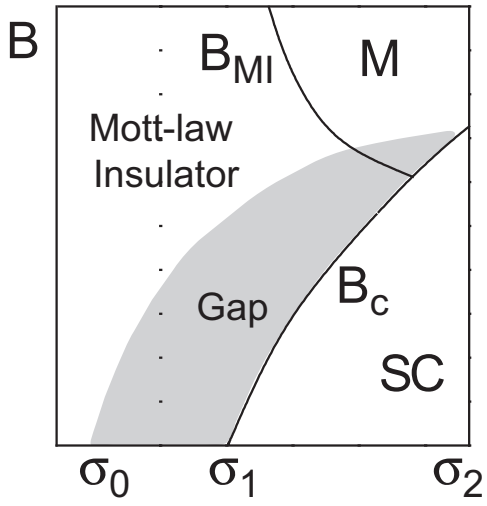

FIG. 1: Schematics of the phase diagram of disordered superconductors in the vicinity of the superconductor-insulator transition as a function of the magnetic field, B, and disorder strength that is characterized by room temperature conductivity, $\sigma \sim k_F l$. In the shaded region the resistiviy exhibits activated behavior with a well defined gap T_I.

The purpose of this Letter is to provide a justification for this picture and to construct the theory of localized Cooper pairs starting from a semi-microscopic model that contains only low energy electrons with BCS-type attraction and a strong random potential which leads to Anderson localization of single-particle states. An important ingredient of the problem is the fractal structure of single-particle wave functions, which sets in on a microscopic scale L_0 determined by the disorder potential and extends to the localization length $L_{\rm loc}$.

It is well established that disorder has little effect on conventional superconductivity[11,12] in the absence of Coulomb repulsion. On the mean-field level (neglect-

ing thermal fluctuations), T_c and the self-consistent BCS gap Δ are affected by the localization and start to decrease only when the effective level spacing in the localization volume, $\delta_L = 1/(\nu_0 L_{\rm loc}^3)$, becomes comparable[11,13,14,15,16] to Δ (here ν_0 is the density of orbital states at the Fermi level). Intuitively, it is clear that the thermodynamics of a strongly disordered superconductor built on localized electron wave functions is practically the same as that of a system separated into compartments (grains) of size $L_{\rm loc}$. In each grain δ_L serves as a low energy cut-off; when it exceeds Δ the superconductivity is destroyed. However, the attraction between electrons persists until δ_L exceeds a high energy cut-off which is typically the Debye frequency, ω_D. The attraction results in pairing of electrons with opposite spins occupying the same localized state. Assuming that the pairing interaction is local and is characterized by a dimensionless coupling $\bar{\lambda}$, the pairing energy, $2\Delta_1$, is proportional to the inverse volume occupied by the state, $\Delta_1 \sim \bar{\lambda}/(\nu_0 V_{\rm eff})$. It is crucial for the following that this volume is parametrically smaller than the 'localization volume' $L_{\rm loc}^3$ due to the fractal nature of the wave functions near the mobility edge $V_{\rm eff} \sim L_0^3 (L_{\rm loc}/L_0)^{D_2}$, where $D_2 < 3$, cf. 17,18. Then the energy scale Δ_1 is parametrically larger than δ_L. Thus, the strength of the disorder is characterized by two relevant energy scales, δ_L and Δ_1.

Here we focus on two limiting cases

$$\Delta \ll \delta_L \ll \omega_D \tag{1}$$

$$\delta_L \ll \Delta \ll \Delta_1 \tag{2}$$

As shown below in the first regime the single-particle gap remains large leading to a gapped insulator. In the second regime the superconductivity persists, but the single-particle gap Δ_1 is much larger than in conventional superconductors. In particular, the ratio of this gap to T_c can be anomalously large. Moreover, in the latter regime the superconducting phase transition is preempted (upon T decrease) by a formation of a "pseudogaped" insulating state similar to the one observed in underdoped cuprates[19].

We assume that a BCS-type attraction between electrons at high energy scales $\sim \omega_D$ is only weakly affected by localization of electron wave functions provided that $\delta_L \ll \omega_D$. The theoretical reason for this is the scaling argument that says that physics at short scales and large energies is not affected by localization as long as $k_F L_{\rm loc} \gg 1$. This is further collaborated by an experimental observation[1,3] that T_c changes little until one gets into a deeply localized regime. In a fermion system with weak attraction one can leave only the pair interaction terms in the Hamiltonian leading to the usual BCS model in the basis of localized electron states[15]:

$$H = \sum_{j\sigma} \epsilon_j c_{j\sigma}^\dagger c_{j\sigma} - \frac{1}{\nu_0} \sum_{j,k} \lambda_{jk} M_{jk} c_{j\uparrow}^\dagger c_{j\downarrow}^\dagger c_{k\uparrow} c_{k\downarrow} \tag{3}$$

where ϵ_j is the single-particle energy of the state j and the matrix elements $M_{jk} = \int d\mathbf{r} \psi_j^2(\mathbf{r}) \psi_k^2(\mathbf{r})$. In Hamiltonian (3) we will also distinguish the off-diagonal dimensionless coupling constant $\lambda_{jk} = \lambda$ for $j \neq k$ from the diagonal one $\lambda_{jj} = \bar{\lambda}$ for the reasons detailed below.

To study the model (3) we need the statistics of single electron states near the 3D Anderson mobility edge. We expect that on average off-diagonal matrix elements, $\bar{M}_{jk}$ with $j \neq k$ have the usual scaling $1/L_{\rm loc}^3$ for the states localized at distances smaller than $L_{\rm loc}$ from each other. In other words we assume that correlations M_{jk} between wave functions of different states are much smaller than individual "inverse participation ratios" (IPRs), $M_{jj} = \int d\mathbf{r} \psi_j^4(\mathbf{r})$, which have the meaning of the inverse volumes of localized states, $V_{\rm eff}$. In fact, extensive numerical studies[17,18] show that a typical IPR, $\bar{M}$, scales as $\bar{M} \approx L_0^{-3} (L_{\rm loc}/L_0)^{-D_2}$, with $D_2 = 1.30 \pm 0.05$.

As discussed above, the thermodynamics of this model should be similar to a collection of grains of size $L_{\rm loc}$ with Hamiltonians

$$H = \sum_{j\sigma} \epsilon_j c_{j\sigma}^\dagger c_{j\sigma} - \sum_{j,k} g_{jk} c_{j\uparrow}^\dagger c_{j\downarrow}^\dagger c_{k\uparrow} c_{k\downarrow} \tag{4}$$

where the average level spacing is $\langle \epsilon_{j+1} - \epsilon_j \rangle = \delta_L$, the off-diagonal part of the interaction has the usual form for a grain, $g_{jk} = g = \lambda \delta_L$ for $j \neq k$, while the diagonal part has an extra term G so that $g_{jj} = g + G = \bar{\lambda} (L_{\rm loc}/L_0)^{-D_2} / (\nu_0 L_0^3)$ due to the fractal nature of the wavefunctions. We have checked that the results described in this Letter are the same (up to numerical factors of order one) for models (3) and (4).

We begin with the insulating region (1) where Cooper interaction can be treated perturbatively[20]. In the first order perturbation theory the minimum energy (counted from the chemical potential), Δ_1, required to add a single electron to the system is

$$\Delta_1 = \frac{\bar{\lambda}}{2\nu_0 L_0^3 (L_{\rm loc}/L_0)^{D_2}} \tag{5}$$

The coupling constant $\bar{\lambda}$ appearing in this equation is not renormalized by Cooper loops: indeed, the Hamiltonians (3) and (4) do not mix unoccupied and doubly occupied (*unblocked*) states with singly occupied (*blocked*) ones. Blocked states do not participate in pair scattering and contribute only their single-particle energy to the Hamiltonian. The additional contribution coming from the diagonal term in (4) is GN_{pairs}, where N_{pairs} is the total number of pairs. Using the fact that the total number of electrons is $2N_{pairs} + N_B$, where N_B is the number of blocked states and shifting single-particle levels $\epsilon_j \to \epsilon_j + G/2$, we can rewrite Hamiltonian (4) as

$$H = \sum_{j\sigma} \epsilon_j c_{j\sigma}^\dagger c_{j\sigma} - g \sum_{j,k} c_{j\uparrow}^\dagger c_{j\downarrow}^+ c_{k\uparrow} c_{k\downarrow} + \sum_B \left(\epsilon_k + \frac{G}{2} \right) \tag{6}$$

Here the first two terms act only on unblocked states, while the summation in the last term is over decoupled blocked states. The renormalization affects only the interacting part which is of a standard BCS form. This

statement is valid for the reduced Hamiltonians (3,4) which contain pair-wise eigenstates only. In general, one would say that our phenomenological Hamiltonians (3,4) contain *two different* coupling constants originating from the competition between Coulomb and electron-phonon interactions – standard BCS coupling λ and the additional "diagonal" one, $\bar{\lambda}$, which characterizes interaction of two electrons in the *same* localized state.

Applying the same arguments to the Hamiltonian (3), we get a single-particle gap that varies from one level to another: $\Delta_1^j = \bar{\lambda} M_{jj}/(2\nu_0)$. The average density of single electron states in a large sample is controlled by the IPR distribution $\mathcal{P}(M)$

$$\nu(\varepsilon) = \nu_0 \int_0^{2\varepsilon\nu_0/\bar{\lambda}} \mathcal{P}(M) dM \tag{7}$$

Scaling theory of localization predicts that near the mobility edge $\mathcal{P}(M)$ acquires a scale-invariant form and this is indeed what was observed in numerical studies[18]. Moreover, these data indicate that the distribution $\mathcal{P}(M)$ decreases fast at $M/\bar{M} \to 0$ so that extended states occur too rare to smear up a gap-like behavior in the density of states (7) with the gap value given by Eq. (5).

We emphasize that the DoS (7) does not contain any "coherence peak" above the gap. The same qualitative behavior of the DoS in the insulating region was obtained[24] by solving numerically BCS mean field equations for the disordered "negative-U" Hubbard model. Evidently, the spectral gap Δ_1 should be associated with the experimentally determined[1,3] activation energy T_I. The gap dependence (5) predicts a moderate increase ($\propto 1/L_{\rm loc}^{D_2}$) of T_I with disorder strength in a complete agreement with the experimental data[1], see Fig. 2. Note that attempts to fit the data with a gap that scales as $\delta_L \propto 1/L_{\rm loc}^3$ have failed spectacularly[1].

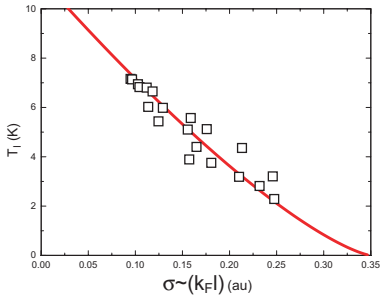

FIG. 2: Experimental values of the gap, T_I (boxes) and a fit to the equation (5) with $L_{loc} \sim (\sigma - \sigma_c)^{-1}$ that involved only the overall scale adjustment[25].

We now turn to the parameter region (2) where one expects a global superconductive coherence. Namely, the condition $\delta_L \ll \Delta$ assures that a large number of eigenstates ψ_j with energies down to $\epsilon_j \sim \Delta$ overlap significantly in the real space, so one can use the standard BCS-type self-consistent gap equation as first argued in Ref. 11.

However, due to an extra cost of creating an unpaired electron, the energy required to add an electron in this regime is no longer equal to the self-consistent gap Δ as in the usual BCS theory. Indeed, because the addition of an electron increases the number of blocked states in (6) by one, we have

$$\Delta_1 = \Delta + \frac{G}{2} \approx \Delta + \frac{\bar{\lambda}}{2\nu_0 L_0^3 (L_{\rm loc}/L_0)^{D_2}} \tag{8}$$

In order to evaluate the energy of pair excitations, i.e. the excitations of the condensate with no unpaired electrons, it is convenient to rewrite Hamiltonian (6) in terms of Anderson's pseudospin-1/2 operators[21] defined on the subspace of unblocked states as $s_j^+ = c_{j\uparrow}^\dagger c_{j\downarrow}^\dagger = (s_j^-)^\dagger$ and $2s_j^z = c_{j\uparrow}^\dagger c_{j\uparrow} + c_{j\downarrow}^\dagger c_{j\downarrow} - 1$. We have

$$H = \sum_j 2\epsilon_j s_j^z - g \sum_{j,k} s_j^+ s_k^- + \sum_B \left(\epsilon_k + \frac{G}{2}\right) \tag{9}$$

In the BCS mean-field approximation eigenstates of (9) correspond to all spins being parallel or antiparallel to the effective magnetic field $B_j = -(2\Delta, 0, 2\epsilon_j)$, where $\Delta = g\sum_j \langle s_j^x \rangle$, leading to a self-consistency condition

$$\frac{2}{g} = \sum_j \frac{e_j}{\sqrt{\epsilon_j^2 + \Delta^2}} \tag{10}$$

where $e_j = 1$ if the spin is against the magnetic field and $e_j = -1$ otherwise.

In the ground state all spins are along their magnetic fields, $e_j = 1$ for all j. The lowest pair excitation corresponds[21,22] to a single spin flip at the Fermi level $\epsilon_0 = 0$ and has an energy $\Delta_2 = 2\Delta$. It also modifies the gap equation since now one of e_j becomes negative, $e_0 = -1$. Because the number of states in the localization volume $L_{\rm loc}^3$ is finite, this modification results[20,23] in a negative correction to the gap: $\delta\Delta = -\delta_L/2$. Thus

$$\Delta_2 = 2\Delta_0 - \delta_L = 2\Delta_0 - \frac{c}{\nu_0 L_{\rm loc}^3} \tag{11}$$

here Δ_0 is the $T = 0$ gap at large L_{loc}, numerical coefficient $c = 1$ for model (4) and $c \sim 1$ for model (3). Note that pair excitations with gap Δ_2 are spinless, whereas single-particle excitations (gap Δ_1) carry spin 1/2. Thus Δ_1 is the *spin gap*, while Δ_2 is the energy gap.

In the regime (2), the typical single-particle gap Δ_1 remains much larger than the gap for pair excitations Δ_2. This leads to the exclusion of single-particle excitations from the thermodynamics at $T \ll \Delta_1$, which results in a modified mean-field result $T_c/\Delta(T=0) = 2[T_c/\Delta(T=0)]_{BCS}$. The actual dependence of T_c on the localization length is not easy to find due to enhanced role of thermal fluctuations near the mobility edge[13,14,15].

We emphasize that $\Delta(T=0)$ does not characterize the spectral gap in the present situation. The most naturally measured (e.g. by tunneling conductance or optical conductivity experiments) spectral parameter is the

single-particle gap Δ_1, which according to Eqs. (8,2) is much larger than T_c. An anomalously large ratio Δ_1/T_c leads to the insulating trend of the resistivity versus temperature behavior in the intermediate temperature range $T_c < T \leq \Delta_1$. This was observed in many strongly disordered superconductors and is especially well-known for underdoped cuprates[26].

The quantitative similarity between $R(T,B)$ behavior in InO_x films and underdoped cuprates noticed in Ref 26 (see also Ref. 27) makes us believe the pseudogap in underdoped cuprates may have a similar origin: pairing of electrons on localized states. The important difference of the cuprates is the d-wave symmetry of the pairing. We plan to address this issue in future work. Suppression of single-particle density of states in the pseudogap regime can be observed by measuring the differential tunneling conductance which we expect to follow the universal IPR distribution $\mathcal{P}(M)$ studied in Ref. 18:

$$\frac{dI}{dV} \propto \left(\frac{d\nu}{d\varepsilon}\right)_{\varepsilon=eV} \propto \mathcal{P}\left(2eV\nu_0/\bar{\lambda}\right) \qquad (12)$$

As emphasized above, the generic features indicating a formation of the novel insulating state near superconductor-insulator transition (such as the resistivity maximum as a function of magnetic field or disorder) were observed in many different materials. However, the details may vary: in InO_x thick (essentially 3D) films the resistivity above the transition has an activated behavior while in very thin (2D) films[2,28] it follows an Efros-Shkovskii law. The theory developed in this Letter is applicable only to 3D systems but it seems likely that a similar physics leads to a weaker but observable effects in 2D films.

In conclusion, weak Anderson insulators with Cooper attraction are shown to possess hard insulating gap whose magnitude is determined by the IPR statistics near the mobility edge. Although this gap is of a superconducting origin, it does not lead to a coherence peak. In the ground-state of this insulator all electrons are paired on individual localized eigenfunctions. When the Fermi-level approaches the mobility edge, superconductive correlations develop between localized pairs. Key features of the predicted superconductive ground-state are an unusually large (compared to T_c) single-particle excitation gap (spin gap) and a pseudogaped regime at temperatures about T_c. These unusual features stem from the fractal nature of localized eigenstates near the mobility edge. We assumed that $\psi_j^2(\mathbf{r})$ of the relevant nearly-critical eigenfunctions have weak mutual correlations. If the correlations are in fact strong[29], the description of the insulating phase is not affected but the ratio $\Delta_1/\Delta \gg 1$ will be significantly reduced. Finally, our theory is based on a phenomenological assumption of an *attractive* sign of the diagonal coupling constant $\bar{\lambda} > 0$. Another interesting situation is realized when $\lambda > 0$, but $\bar{\lambda} < 0$. In this case we expect a formation of "effective magnetic impurities" and strong suppression of T_c. We plan to consider this situation separately.

We are grateful to B. L. Altshuler, T. I. Baturina, V. F. Gantmakher, A. S. Ioselevich, V. E. Kravtsov, A. Millis, A. D. Mirlin, M. Mueller, Z. Ovadyahu, D. Shahar for useful discussions. This research was supported by NSF grant DMR 0210575, by NATO CLG grant 979979, by RFBR grants 04-02-16348, 04-02-08159 and by the program "Quantum Macrophysics" of RAS.

[1] D.Shahar and Z.Ovadyahu, Phys. Rev. B **46**, 10917 (1992)
[2] Y.Liu *et al*, hys. Rev. B **47**, 5931 (1993).
[3] D.Kowal and Z.Ovadyahu, Sol.St.Com. **90**, 783 (1994).
[4] V. F. Gantmakher *et al* Pis'ma ZhETF **71**, 693 (2000).
[5] V. Butko and P. Adams, *Nature*, **409**, 161 (2001).
[6] T. I. Baturina *et al*, Pis'ma ZhETF **79** 416 (2004).
[7] G. Sambandamurthy *et al*, Phys. Rev. Lett. **92**, 107005 (2004).
[8] G. Sambandamurthy *et al*, cond-mat/0403480.
[9] M. A. Steiner and A. Kapitulnik, cond-mat/0406227.
[10] V. F. Gantmakher *et al*, JETP Letters **68**, 345 (1998); V. F. Gantmakher, Physics-Uspekhi **41**, 214 (1998).
[11] P.W. Anderson, J.Phys.Chem.Solids **11**, 26 (1959).
[12] A.A. Abrikosov and L.P. Gorkov, Sov. Phys. JETP 8 (1958) 1090.
[13] L. N. Bulaevsky and M. V. Sadovsky, JETP Letters **39**, 640 (1984).
[14] A. Kapitulnik and G. Kotliar, Phys. Rev. Lett. **54**, 473 (1985).
[15] S.-K. Ma and P.A. Lee, Phys. Rev. B **32**, 5658 (1985).
[16] A.I.Larkin, Ann.Phys. (Leipzig) **8**, 507 (1999).
[17] D.A.Parshin and H.R.Schober, Phys. Rev. Lett. **83**, 4590 (1999).
[18] A.Mildenberger, F.Evers and A.D.Mirlin, Phys. Rev. B **66**, 033109 (2002).
[19] K. M. Lang, *et al* Nature, 415 412 (2002).
[20] K.A.Matveev and A.I.Larkin, Phys. Rev. Lett. **78**, 3749 (1997).
[21] P. W. Anderson: Phys. Rev. **112**, 1900 (1958).
[22] J. Bardeen, L.N. Cooper, and J.R. Schriefer, Phys. Rev. **108** 1175 (1957).
[23] E. A. Yuzbashyan, A. A. Baytin, and B. L. Altshuler. Phys. Rev. B 71, 094505 (2005).
[24] A.Ghosal, M.Randeria and N.Trivedi, Phys. Rev. B **65**, 014501 (2001).
[25] The fit was communicated to us by Z. Ovadyahu.
[26] M. A. Steiner, G. Bobinger and A. Kapitulnik, cond-mat/0406232.
[27] X. F. Sun, K. Segawa and Y. Ando, cond-mat/0502223.
[28] T.I.Baturina *et al*, cond-mat/0309281, version 1.
[29] V.E.Kravtsov, private communication.